

Surface plasmon lifetime in metal nanoshells

A. S. Kirakosyan,^{1,2} M. I. Stockman,³ and T. V. Shahbazyan¹

¹*Department of Physics, Jackson State University, Jackson, MS 39217 USA*

²*Department of Physics, Yerevan State University, Yerevan, 0025 Armenia*

³*Department of Physics and Astronomy,
Georgia State University, Atlanta, GA 30303 USA*

Abstract

The lifetime of localized surface plasmon plays an important role in many aspects of plasmonics and its applications. In small metal nanostructures, the dominant mechanism restricting plasmon lifetime is size-dependent Landau damping. We performed quantum-mechanical calculations of Landau damping of a surface plasmon in a metal nanoshell. In contrast to the conventional picture based on the electron surface scattering, we found that the damping rate *vanishes* in the limit of thin nanoshell. The physical origin of this behavior is the reduced magnitude of bright surface plasmon electric field inside the metal shell. We also found that, due to electron scattering on two metal surfaces, the damping rate exhibits pronounced *quantum beats* with changing shell thickness.

I. INTRODUCTION

Lifetime of localized surface plasmon (SP) in metal nanostructures is one of fundamental problems in plasmonics that has been continuously addressed for more than 40 years [1, 2]. The importance of this issue stems from one of the major objectives of plasmonics – generation of extremely strong local fields at the nanoscale. The range of physical phenomena and applications related to this goal cuts across physics, chemistry, biology, and device applications. A small sample of examples includes SP-enhanced spectroscopies of molecules near metal nanostructures, such as surface-enhanced Raman scattering (SERS) and fluorescence resonance energy transfer (FRET) and their numerous biomedical applications [3], focusing of extremely large electric fields in metal nanoparticle (NP) clusters [4], and quantum coherent SP generation in nanostructures (SPASER) [5]. High Ohmic losses in bulk metal due to strong electron-phonon interactions impose limitation on the quantum yield of metal-based plasmonic devices, which can, to some extent, be remedied by reducing the metal component size. However, at the lengthscale below ~ 10 nm, new limitations on SP lifetime and, consequently, on quantum yield arise due to quantum-size effects. Among those, the most important is the Landau damping (LD) of SP – decay of SP into the Fermi sea electron-hole pair. This process is made possible by relaxation of the momentum conservation due to electron surface scattering. The electron-hole momentum uncertainty, $\delta p \sim \hbar/a$, where a is the characteristic size of nanostructure, translates into the corresponding energy relaxation scale, $\delta E \sim p \delta p/m$, m being electron mass in metal, and this leads to the following estimate of SP lifetime,

$$\Gamma \sim A \frac{v_F}{a}, \quad (1)$$

where v_F is the electron Fermi velocity (hereafter we set $\hbar = 1$). The first explicit quantum-mechanical calculation of Γ for spherical NP by Kawabata and Kubo [1] confirmed the estimate (1) with a replaced by particle radius R and, for NP in vacuum, yielded the value $A = 3/4$. While the subsequent studies indicated that the coefficient A varies in the range (0.5-2.0) depending on dielectric constant and chemical composition of surrounding medium, the size dependence (1) was thoroughly confirmed experimentally for *spherical* particles [2]. The corresponding quality factor,

$$Q = \frac{\omega_{sp}}{\Gamma}, \quad (2)$$

where ω_{sp} is SP frequency, decreases linearly with R . This causes a rapid reduction of, e.g., SERS enhancement factor, $M \propto Q^4$, while the other quantum-size effects, such as electron density spillover or surface screening, play a subdominant role [6].

The above qualitative arguments have been subsequently used for estimates of SP lifetime in nanostructures of various shapes, notably in metal nanoshells [7]. The *single-electron* picture of SP damping, based solely on surface scattering, inevitably leads to a SP damping of the form (1), with a replaced by the *smallest* spatial scale of a confined nanostructure. For example, in a nanoshell with shell thickness d , the characteristic electron scattering length is $\sim d$, and Eq. (1) predicts a very short SP lifetime for thin nanoshells. First attempts to measure SP lifetime in nanoshells seemed to be consistent with Eq. (1) with estimated values $A = 2.0$ [8] and $A = 0.5$ [9]. However, more recent systematic studies of optical spectra of single gold nanoshells indicated no size-dependence at all ($A = 0$) for the extracted SP lifetime [10].

There is also a physical argument that renders Eq. (1) invalid for nanostructures of general shape. Indeed, LD is a *many-body* phenomenon, rather than a single-particle one, and it involves the SP own electric field by which an electron-pair is excited. Therefore, the SP lifetime must be highly sensitive to the field *magnitude* inside the NP. Note that for a solid sphere, the SP electric field magnitude is a frequency-dependent constant that is independent of NP radius. This is the reason why Eq. (1) holds remarkably well for spherical NP in a very wide range of their radii, from several tens of nm down to nanometer-sized small clusters [2]. In contrast, for other NP shapes, the magnitude of SP electric field inside the NP can change with NP size. As we show below, the latter effect can, in fact, be much stronger than surface scattering contribution, resulting in a drastically different, from Eq. (1), SP damping rate.

In this paper, we calculate the LD of bright SP modes in a metal nanoshell with dielectric core. We demonstrate that in the limit of *thin* nanoshell, the LD rate *vanishes* linearly with the nanoshell thickness d . Furthermore, for small overall nanoshell sizes, SP lifetime exhibits *quantum beats* as a function of shell thickness, caused by the interference between electron scattering amplitudes near inner and outer nanoshell boundaries. We also show that despite the redshift of the SP frequency, the nanoshell quality factor *increases* with decreasing d . The latter finding indicates that, with appropriate choice of geometry, the quantum-size limitations imposed on plasmonics can be sidelined, and the quantum yield of even small

plasmonic devices can be made limited only by the Ohmic losses.

In Section II we obtain a formal expression for LD rate in terms of plasmon eigenmodes in metal nanoshell with dielectric core. In Section III we evaluate of nanoshell internal energy, and in Section IV we evaluate the dissipated power by calculating the imaginary part of electron polarization operator in semiclassical approximation. The analysis and numerical results are presented in Section V, and Section VI concludes the paper.

II. PLASMON EIGENMODES IN A NANOSHELL

We consider metal nanoshell with inner and outer radii R_1 and R_2 , respectively, in a medium with dielectric constant ε_d . In long-wave approximation, the local potential $\Phi(\mathbf{r})$ is determined from self-consistent equation [11]

$$\Phi(\mathbf{r}) = \varphi(\mathbf{r}) + \int d\mathbf{r}_1 d\mathbf{r}_2 U(\mathbf{r} - \mathbf{r}_1) P(\mathbf{r}_1, \mathbf{r}_2) \Phi(\mathbf{r}_2), \quad (3)$$

where $\varphi \propto r^L Y_{LM}(\hat{\mathbf{r}})$ is an external potential ($Y_{LM}(\hat{\mathbf{r}})$ are spherical harmonics), $P = P' + iP''$ is polarization operator, and $U(r)$ is Coulomb potential. We are interested in plasmonic eigenmodes that are described by Eq. (3) without external potential, which we write as

$$(1 + 4\pi\hat{\chi})\Phi = 0, \quad (4)$$

where $\hat{\chi}$ is a susceptibility operator defined as

$$\hat{\chi}\Phi(\mathbf{r}) = e^2 \int d\mathbf{r}_1 d\mathbf{r}_2 G(\mathbf{r} - \mathbf{r}_1) P(\mathbf{r}_1, \mathbf{r}_2) \Phi(\mathbf{r}_2), \quad (5)$$

and $G(r) = -U(r)/4\pi e^2 = -1/4\pi r$. For optical frequencies, the real part of polarization operator can be approximated by its local limit and decomposed into the core, metal and outside dielectric contributions, $P' = P'_c + P'_m + P'_d$, with

$$P'_i(\mathbf{r}, \mathbf{r}') = e^{-2} \nabla [\chi_i(r) \nabla \delta(\mathbf{r} - \mathbf{r}')] , \quad (6)$$

where $\chi_c(r) = \chi_c \theta(R_1 - r)$, $\chi_m(r) = \chi_m \theta(r - R_1) \theta(R_2 - r)$, $\chi_d(r) = \chi_d \theta(r - R_2)$ are local susceptibilities, $\chi_i = (\varepsilon_i - 1)/4\pi$.

In the absence of damping, plasmon energies are obtained by setting $P'' = 0$ and solving Eq. (4) in the basis of eigenfunctions of composite operator $\hat{\chi}' = \hat{G}\hat{P}'$: $\hat{\chi}' F_{LM} = \lambda_L F_{LM}$. The eigenvalues are found by setting

$$1 + 4\pi\lambda_L = \varepsilon_m + B \pm \sqrt{B^2 + C} = 0, \quad (7)$$

where

$$B = \frac{L\varepsilon_{cm} - (L+1)\varepsilon_{md}}{2(2L+1)}, \quad C = \frac{L(L+1)}{(2L+1)^2}(1 - \kappa^{2L+1})\varepsilon_{md}\varepsilon_{cm}, \quad (8)$$

$\kappa = R_1/R_2$ is the shell aspect ratio, and we denote $\varepsilon_{\alpha\beta} = \varepsilon_\alpha - \varepsilon_\beta$. The eigenfunctions $F_{LM} = F_L(r)Y_{LM}(\hat{\mathbf{r}})$ are obtained from continuity of $F_L(r)$ across all interfaces

$$\begin{aligned} F_L^{(c)} &= (\kappa^L + \eta_L) \left(\frac{r}{R_1}\right)^L, \quad F_L^{(m)} = \left(\frac{r}{R_2}\right)^L + \eta_L \left(\frac{R_1}{r}\right)^{L+1}, \\ F_L^{(d)} &= (1 + \kappa^{L+1}\eta_L) \left(\frac{R_2}{r}\right)^{L+1}, \quad \eta_L = -\frac{L\varepsilon_{cm}\kappa^L}{L\varepsilon_{cm} + (2L+1)\varepsilon_m}. \end{aligned} \quad (9)$$

Note that F_α satisfy orthogonality condition $\langle \mu | \hat{P}' | \nu \rangle = \delta_{\mu\nu} P'_\mu$; μ is composite index (LMj) , where $j = \pm$ in Eq. (7) is plasmon type (bright or dark, respectively).

Plasmon decay into electron-hole pairs is described by incorporating the imaginary part of polarization operator into Eq. (4), $\hat{\chi} = \hat{G}\hat{P} = \hat{G}\hat{P}' + i\hat{G}\hat{P}''$, as follows. First, Eq. (4) is multiplied from left by $\langle \mu | \hat{P}'$ and, using that $\hat{P}'\hat{\chi} = \hat{\chi}'\hat{P}$, we obtain

$$(1 + 4\pi\lambda_\mu) \langle \mu | \hat{P}' | \Phi \rangle + 4\pi i\lambda_\mu \langle \mu | \hat{P}'' | \Phi \rangle = 0. \quad (10)$$

Then, expanding the potential over eigenstates of $\hat{\chi}'$, $\Phi = \sum C_L^j F_{LM}^j$, we get

$$(1 + 4\pi\lambda_L^j) P_L^j C_L^j + 4\pi i\lambda_L^j \sum_{L'j'} P_{LL'}^{jj'} C_{L'}^{j'} = 0, \quad (11)$$

where

$$P_{LL'}^{jj'} = \frac{1}{2L+1} \sum_{MM'} \langle LMj | P'' | L'M'j' \rangle \quad (12)$$

is the reduced, due to spherical symmetry, matrix element of $\hat{P}''$. Admixture of plasmon modes by P'' being weak, the non-diagonal terms in Eq. (11) can be neglected. The new resonance condition takes the form $1 + 4\pi(\lambda_L^j + \delta\lambda_L^j) = 0$, where $\delta\lambda_L^j = i\lambda_L^j P_{LL}^{jj} / P_L^j$ is an *imaginary* correction to the eigenvalue. Its appearance implies a shift of eigenmode frequency into the complex plane, $\lambda_L(\omega_L + i\Gamma_L/2) = \lambda_L(\omega_L) + i(\Gamma_L/2) [\partial\lambda_L(\omega_L)/\partial\omega_L]$. Equating the last term to $\delta\lambda_L$, we obtain the following expression for the decay rate

$$\Gamma_L = \frac{2\lambda_L P_{LL}''(\omega_L)}{\frac{\partial\lambda_L}{\partial\omega_L} P_L'(\omega_L)} = \frac{\mathcal{Q}_L}{\mathcal{U}_L}, \quad (13)$$

where we suppressed bright/dark indices. Here $\mathcal{Q}_L$ is the dissipated power of plasmon eigenmode,

$$\mathcal{Q}_L = -\omega_L P''_{LL} = \text{Re} \int d\mathbf{r} \mathbf{J}_{LM} \cdot \mathbf{E}_{LM}, \quad (14)$$

$\mathbf{E}_{LM} = -\nabla F_{LM}$ and $\mathbf{J}_{LM}$ being the plasmon electric field and the current, respectively, and

$$\mathcal{U}_L = -\frac{\omega_L}{2\lambda_L} \frac{\partial \lambda_L}{\partial \omega_L} P'_L = \frac{1}{8\pi} \frac{\omega_L}{\lambda_L} \frac{\partial \lambda_L}{\partial \omega_L} \int d\mathbf{r} [\varepsilon(r) - 1] \mathbf{E}_{LM}^2, \quad (15)$$

is the plasmon eigenmode energy stored in a metal-dielectric composite.

III. CALCULATION OF EIGENMODE ENERGY

Consider first the plasmon eigenmode energy, $\mathcal{U}^L$. The electric field integral in Eq. (15) reduces to boundary contribution,

$$\int d\mathbf{r} [\varepsilon(r) - 1] \mathbf{E}_{LM}^2 = -4\pi \left[R_1^2 F_L(R_1) \sigma_L^{(1)} + R_2^2 F_L(R_2) \sigma_L^{(2)} \right], \quad (16)$$

where $\sigma_L^{(i)}$ are surface charges at i th interface. Those are given by $\sigma_L^{(1)} = \epsilon_{cm} \mathcal{E}_L(R_1)/4\pi\epsilon_c$ and $\sigma_L^{(2)} = \epsilon_{md} \mathcal{E}_L(R_2)/4\pi\epsilon_d$, where $\mathcal{E}_L(R_i) = -\partial F_L(R_i)/\partial R_i$ are the interfacial electric fields (on metal side). The prefactor in Eq. (15) can be split as

$$\frac{\omega_L}{\lambda_L} \frac{\partial \lambda_L}{\partial \omega_L} = -A_L \omega_L (\partial \epsilon'_m / \partial \omega_L), \quad (17)$$

where

$$A_L = -\lambda_L^{-1} (\partial \lambda_L / \partial \epsilon_m) = 4\pi (\partial \lambda_L / \partial \epsilon_m). \quad (18)$$

For metal shell, we use the Drude dielectric function $\varepsilon_m = \varepsilon_{db} - \omega_p^2/\omega(\omega + i\gamma)$, where ε_{db} is the interband dielectric function due to d -band to sp -band transitions, ω_p is bulk plasmon frequency, and γ is the bulk damping rate. Then we have $\omega_L (\partial \varepsilon'_m / \partial \omega_L) = 2(\omega_L/\omega_p)^2 [(\omega_L/\omega_p)^2 + (\gamma/\omega_p)^2]^{-2} \approx 2(\omega_p/\omega_L)^2$ for optical frequencies ($\omega_L \gg \gamma$). Putting all together, we finally obtain

$$\mathcal{U}_L = \frac{A_L}{4\pi e^2} \left(\frac{\omega_p}{\omega_L} \right)^2 \left[\frac{\epsilon_{md}\epsilon_m}{L+1} \mathcal{E}_L^2(R_2) R_2^3 + \frac{\epsilon_{mc}\epsilon_m}{L} \mathcal{E}_L^2(R_1) R_1^3 \right], \quad (19)$$

where we used $\mathcal{E}_L(R_1) = -L(\varepsilon_c/\varepsilon_m R_1) F_L(R_1)$ and $\mathcal{E}_L(R_2) = (L+1)(\varepsilon_d/\varepsilon_m R_2) F_L(R_2)$.

The dependence of dipole SP energy on aspect ratio is plotted in Fig. 1 for gold nanoshell in vacuum, and for gold nanoshell with Au₂S core in water. Importantly, with increasing core radius, the stored energy remains comparable to (vacuum) or exceeds (dielectric) that in a solid particle. This can be understood by noting that a nanoshell is analogous to a (high-frequency) capacitor formed by two concentric spherical surfaces. For bright dipole mode, the opposite charges are located in *different* hemispheres, so the energy is proportional to the core-shell particle volume; a dielectric core then leads to an increase of the stored energy. In contrast, for dark modes, the opposite charges are placed at inner and outer boundaries, so the energy vanishes as with the volume between capacitor plates decreases.

Simple expressions can be obtained for a metal shell in vacuum, $\varepsilon_c = \varepsilon_d = 1$. The corresponding eigenvalues are given by

$$\lambda_L = A_L(\varepsilon_m - 1)/4\pi, \quad A_L = \frac{1}{2} \left[1 \mp \sqrt{1 + 4L(L+1)\kappa^{2L+1}/(2L+1)} \right], \quad (20)$$

yielding the well known resonance frequencies $\omega_L/\omega_p = \sqrt{A_L[1 + A_L(\varepsilon_{db} - 1)]^{-1}}$. In this case, the integration in Eq. (15) is effectively restricted to metal region and we recover the known expression for time-averaged internal energy in dispersive media

$$\mathcal{U}_L = \frac{\omega_L}{8\pi} \frac{\partial \varepsilon'_m}{\partial \omega_L} \int_m d\mathbf{r} \mathbf{E}_{LM}^2 = \frac{1}{8\pi} \int d\mathbf{r} \left[\frac{\partial \omega_L \varepsilon'(\omega_L, r)}{\partial \omega_L} \right] \mathbf{E}_{LM}^2 \quad (21)$$

where we used $\nabla \cdot (\varepsilon \mathbf{E}_{LM}) = 0$. Then Eq. (19) can be evaluated using eigenfunctions (9) with $\eta_L = L\kappa^L [L + 1 - (2L + 1)A_L]^{-1}$. The result reads

$$\mathcal{U}_L = (1 - \kappa^{2L+1}) \frac{LR_2}{4\pi e^2} \left(\frac{\omega_p}{\omega_L} \right)^2 \left[1 + \frac{L(L+1)\kappa^{2L+1}}{[L + 1 - (2L + 1)A_L]^2} \right]. \quad (22)$$

For thin shells, $d/R_2 = (1 - \kappa) \ll 1$, we have $(\omega_L/\omega_p)^2 \approx A_L \approx (1 - \kappa)L(L+1)/(2L+1)$ (for bright plasmon mode), so that $\mathcal{U}_L \approx R_2(2L+1)^3/4\pi(L+1)^2$, while for solid particle we have $\mathcal{U}_L^p = R_2(L\varepsilon_{db} + L + 1)/4\pi$, yielding $\mathcal{U}_L/\mathcal{U}_1^p \approx 0.6$ [note that $\mathcal{U}_L$ vanishes in the d.c. limit $\omega/\gamma \lesssim 1$ corresponding to $d/R_2 \lesssim (\gamma/\omega_p)^2$].

IV. CALCULATION OF DISSIPATED POWER

We now turn to the calculation of dissipated power, $\mathcal{Q}_L = -\omega_L P''_{LL}$. Within RPA for imaginary part of electron polarization operator, it is given by

$$\mathcal{Q}_L = \frac{2\pi\omega_L}{2L+1} \sum_{M\alpha\alpha'} |\langle \alpha | F_{LM} | \alpha' \rangle|^2 \delta(\epsilon_\alpha - \epsilon_{\alpha'} + \omega_L), \quad (23)$$

where the sums run over occupied (α) and unoccupied (α') electronic states with wave-functions $\psi_\alpha(\mathbf{r}) = \psi_{nl}(r)Y_{lm}(\hat{\mathbf{r}})$ and energies ϵ_{nl} (n is radial quantum number), and the factor 2 accounts for the spin degeneracy. The angular part factorizes out and Eq. (23) can be written as

$$\mathcal{Q}_L = 2\pi\omega_L \sum_{nn'l'l'} a_{ll'}^L |M_{nl,n'l'}^L|^2 \delta(\epsilon_{nl} - \epsilon_{n'l} + \omega_L), \quad (24)$$

where $M_{nl,n'l'}^L = \langle nl|F_L|n'l'\rangle$ and $a_{ll'}^L = \frac{1}{2L+1} \sum_{Mmm'} |\int d\Omega Y_{LM} Y_{lm}^* Y_{l'm'}|^2$ are radial and angular contribution, respectively. The latter is non-zero only for $l = l' \pm L$, and for typical $l, l' \gg L$, can be approximated as $a_{ll'}^L \approx \delta_{ll'}/2\pi$.

Let us first qualitatively discuss the LD of the $L = 1$ SP in a solid particle of radius R . In a finite system, the dipole matrix element, $\langle nl|r|n'l'\rangle = \frac{1}{m\omega_1} \langle nl|p|n'l'\rangle$ is non-zero because the momentum is not a good quantum number. For low-energy transitions across the Fermi level ($\omega_L \ll E_F$) we have $\langle nl|p|n'l'\rangle \sim p_F/(n-n') \sim \epsilon_0 p_F/\omega_1$, where ϵ_0 is separation between levels at the Fermi level with the *same* (or fixed difference of) l ($\epsilon_0 = \hbar v_F/R$ for a solid particle). We then obtain $\langle nl|p|n'l'\rangle^2 \sim (\epsilon_0 p_F)^2/m^2\omega_1^4$. The sums over n, n' in Eq. (24) are transformed into energy integral over a strip of width ω_1 around the Fermi level, resulting in a factor $\omega_1 \rho_l^2$, where $\rho_l \sim \epsilon_0^{-1}$ is the partial density of states (DOS) at the Fermi level. Finally, the sums over angular momenta is dominated by the maximal l in a quantum well of width R , $l_{max} \sim p_F R$, contributing another factor of $(p_F R)^2$. Putting all together, we obtain $\mathcal{Q}_1 \sim R^2 (E_F/\omega_1)^2$. Note that the level spacing ϵ_0 *cancels out*, and dissipated power is determined by the nanoparticle *surface area*. At the same time, the energy of dipole plasmon (with $F_1 = r$) is proportional to the particle *volume*, $W_1 \sim (R^3/e^2)(\omega_p/\omega_1)^2$, yielding $\Gamma \sim (E_F/\omega_p)^2 (e^2/R) \sim v_F/R$. We emphasize that the $1/R$ dependence of Γ originates from the distribution of surface charges rather than from quantum-size corrections. The dissipated power is simply proportional to the surface area available for electron scattering, but it is insensitive to the structure of electron energy spectrum, as indicated by the cancellation of electronic DOS in the transition matrix elements. A similar cancellation takes place also for a shell geometry so that $\mathcal{Q}_L$ is also proportional to its surface area. On the other hand, the bright plasmon mode energy $\mathcal{U}_L$ is proportional to the core-shell particle volume, so one would expect a similar size-dependence of Γ as for a solid particle of the same overall size. However, as we show below, LD damping in thin nanoshells is even weaker to due the enhancement of screening, caused by the SP frequency redshift, that pushes the bright SP

electric field out of the metal shell region.

To evaluate $\mathcal{Q}_L$, we represent nanoshell confining potential as 3D quantum well with hard boundaries at R_1 and R_2 , $V(r) = V_0\theta(R_1 - r)\theta(r - R_2)$. The matrix element of plasmon potential F_{LM} is dominated by surface contribution, $\langle\alpha|F_{LM}|\alpha'\rangle = \frac{1}{\omega_L^2}\langle\alpha|[H[H, F_{LM}]]|\alpha'\rangle \approx \frac{1}{m\omega_L^2}\langle\alpha|\nabla F_{LM} \cdot \nabla V|\alpha'\rangle$, and, after separating out angular part, takes the form $M_{nl,n'l'}^L = \frac{V_0}{m\omega_L^2}[\psi_{nl}(R_1)\psi_{n'l'}(R_1)\mathcal{E}_L(R_1) - \psi_{nl}(R_2)\psi_{n'l'}(R_2)\mathcal{E}_L(R_2)]$. For deep enough well, matching of wave-functions across the well boundaries gives $\sqrt{2mV_0}\psi_{nl}(R_i) \approx -\psi'_{nl}(R_i)$ (here prime stands for derivative), and the matrix element takes the form

$$M_{nl,n'l'}^L = \frac{1}{2m^2\omega_L^2}[\psi'_{nl}(R_1)\psi'_{n'l'}(R_1)\mathcal{E}_L(R_1) - \psi'_{nl}(R_2)\psi'_{n'l'}(R_2)\mathcal{E}_L(R_2)]. \quad (25)$$

The two terms describe excitation, by the SP electric field, of a Fermi sea electron-hole pair with the momentum transfer to inner and outer boundaries. Correspondingly, $\mathcal{Q}_L$ can be decomposed as $\mathcal{Q}_L = \mathcal{Q}_L^{11} + \mathcal{Q}_L^{22} - 2\mathcal{Q}_L^{12}$, where

$$\mathcal{Q}_L^{ij} = \frac{1}{4m^4\omega_L^3}\mathcal{E}_L(R_i)\mathcal{E}_L(R_j)\sum_{lnn'}\psi'_{nl}(R_i)\psi'_{n'l}(R_i)\psi'_{nl}(R_j)\psi'_{n'l}(R_j)\delta(\epsilon_{nl} - \epsilon_{n'l} + \omega_L), \quad (26)$$

and we used that $a_{ll'}^L \approx \delta_{ll'}l/2\pi$. For typical electron energies $\epsilon_{nl} \sim E_F$, we can use semiclassical approximation for electron wave-functions, $\psi_{nl}(r) = \sqrt{4m/p_l\tau_l} \sin \int_r^{R_2} p_l dr$, where $p_l(\epsilon, r) = \sqrt{2m\epsilon - (l + 1/2)^2/r^2}$, and $\tau_l(\epsilon)$ is the period of classical motion between two turning points. Consider first the outer surface contribution, $\mathcal{Q}_L^{22}$. In this case $\psi'_{nl}(R_2) = -\sqrt{4mp_l(R_2)/\tau_l}$. When plasmon energy ω_L is larger than fixed- l level spacing in the nanoshell, $\epsilon_0 = v_F/d$, the sums in Eq. (26) can be replaced by integrals, $\sum_n \rightarrow \int d\epsilon \rho_l(\epsilon)$ (with $\epsilon < E_F, \epsilon' > E_F$), where the partial DOS $\rho_l(\epsilon) = \partial n / \partial \epsilon_{nl}$ is related to the classical period as $\rho_l = \tau_l / 2\pi$. The result reads

$$\mathcal{Q}_L^{22} = \frac{\mathcal{E}_L^2(R_2)}{\pi^2 m^2 \omega_L^3} \sum_l l \int_{E_F - \omega_L}^{E_F} d\epsilon p_l(\epsilon, R_2) p_l(\epsilon + \omega_L, R_2). \quad (27)$$

Note that the partial DOS cancels out and $\mathcal{Q}_L^{22}$ depends only on electron and hole velocities at the outer surface R_2 . In the energy integral, the integration variable is first shifted as $\epsilon \rightarrow E_F + \epsilon - \omega_L/2$, where ϵ now changes in the interval $(-\omega_L/2, \omega_L/2)$, and then rescaled to $x = \epsilon/\omega_L$. The sum over l is replaced by integral restricted by maximal value $l \sim p_F R_2$ that is determined by the condition $p_l(\epsilon, R_2) \geq 0$. After rescaling to $s = l^2/(p_F R_2)^2$, it

contributes a factor proportional to the outer surface area. The result reads

$$\mathcal{Q}_L^{22} = \frac{E_F^2 R_2^2}{\pi^2 \omega_L^2} \mathcal{E}_L^2(R_2) g(\omega/E_F), \quad (28)$$

where $g(\xi) = 2 \int_{-1/2}^{1/2} dx \int ds f(\xi, x, s)$, with $f(\xi, x, s) = \sqrt{(1 + \xi x - s)^2 - \xi^2/4}$, is dimensionless function of order 1 normalized to $g(0) = 1$.

Turning to the inner surface term, $\mathcal{Q}_L^{11}$, the main contribution into the r.h.s. of Eq. (26) comes from the terms where the turning point lies outside of potential well, i.e., $p_l(\epsilon, R_1) \geq 0$ (otherwise $\psi_{nl}(R_1)$ are exponentially small). In this case, we have $\psi'_{nl}(R_1) = -(-1)^n \sqrt{4mp_l(R_1)/\pi}$, where the sign factor $(-1)^n$ accounts for the *parity* of electron wave-function with $n - 1$ nodes between R_1 and R_2 . The rest of the calculation is carried in a similar way, and the result,

$$\mathcal{Q}_L^{11} = \frac{E_F^2 R_1^2}{\pi^2 \omega_L^2} \mathcal{E}_L^2(R_1) g(\omega/E_F), \quad (29)$$

is proportional to the inner surface area.

Consider now the interference term $\mathcal{Q}_L^{12}$. Using the above boundary values of $\psi'_{nl}(R_i)$, we write

$$\mathcal{Q}_L^{12} = \frac{4\mathcal{E}_L(R_1)\mathcal{E}_L(R_2)}{m^2\omega_L^3} \sum_{lnn'} \frac{l(-1)^{n-n'}}{\tau_l(\epsilon_{nl})\tau_l(\epsilon_{n'l})} \mathcal{F}_l(\epsilon_{nl}, \epsilon_{n'l}) \delta(\epsilon_{nl} - \epsilon_{n'l} + \omega_L), \quad (30)$$

where $\mathcal{F}_l(\epsilon_{nl}, \epsilon_{n'l}) = \sqrt{p_l(\epsilon_{nl}, R_1)p_l(\epsilon_{n'l}, R_1)p_l(\epsilon_{nl}, R_2)p_l(\epsilon_{n'l}, R_2)}$. The alternating sign reflects the *parity* of excited electron-hole state. As ω_L changes (e.g., with changing aspect ratio), the relative parity of electron and hole states separated by energy ω_L changes too, leading to a different sequence of alternating signs in the sum in Eq. (30). This leads to oscillatory behavior of $\mathcal{Q}_L^{12}$. The number of states contributing into the sum on Eq. (30) being large, the oscillations are relatively weak and can be accounted, in the continuum limit, by a replacement $(-1)^{n-n'} = \cos \pi(n - n') = \cos \left[\pi \int_{\epsilon}^{\epsilon'} d\epsilon \rho_l(\epsilon) \right]$. Then $\mathcal{Q}_L^{12}$ takes the form

$$\mathcal{Q}_L^{12} = \frac{\mathcal{E}_L(R_1)\mathcal{E}_L(R_2)}{\pi^2 m^2 \omega_L^3} \sum_l l \int_{E_F - \omega_L}^{E_F} d\epsilon \mathcal{F}_l(\epsilon, \epsilon + \omega_L) \cos \left[\pi \int_{\epsilon}^{\epsilon + \omega_L} d\epsilon' \rho_l(\epsilon') \right], \quad (31)$$

where l is restricted by the condition $p_l(\epsilon, R_1) \geq 0$. After shifting integration variables as $\epsilon \rightarrow E_F + \epsilon - \omega_L/2$ and $\epsilon' \rightarrow E_F + \epsilon + \epsilon'$ and rescaling, Eq. (30) takes the form

$$\mathcal{Q}_L^{12} = \frac{R_1^2 E_F^2}{\pi^2 \omega_L^2} \mathcal{E}_L(R_1) \mathcal{E}_L(R_2) G(\omega_L/E_F), \quad (32)$$

where

$$G(\xi) = 2 \int_{-1/2}^{1/2} dx \int ds \sqrt{f(\xi, x, s) f(\xi, x, \kappa^2 s)} \cos \left[\pi \omega_L \int_{-1/2}^{1/2} dx' \rho_l [E_F [1 + \xi(x + x')]] \right], \quad (33)$$

and the partial DOS is given by $\rho_l(\epsilon) = \frac{m}{\pi} \int_{R_1}^{R_2} \frac{dr}{p_l(\epsilon, r)} = (1/2\pi\epsilon) [R_2 p_l(\epsilon, R_2) - R_1 p_l(\epsilon, R_1)]$ with $l = \sqrt{s}(p_F R_1)$. For $\omega/E_F \ll 1$, the x' -integrals is easily evaluated, yielding

$$G(\xi) = 2 \int_{-1/2}^{1/2} dx \int_0^{1+\xi x} ds \sqrt{f(\xi, x, s) f(\xi, x, \kappa^2 s)} \cos [w(\xi, x, s) \omega_L / \epsilon_0], \quad (34)$$

where $w(\xi, x, s) = \sqrt{f(\xi, x, \kappa^2 s)} - \kappa \sqrt{f(\xi, x, s)}$ with $f(\xi, x, s) \approx 1 + \xi x - s$ (here $\epsilon_0 = v_F / R_2$). Rescaling s by $1 + \xi x$, Eq. (34) factorizes as $G(\xi) = \int_{-1/2}^{1/2} dx (1 + \xi x)^{3/2} S(\xi, x)$, where

$$S(\xi, x) = 2 \int_0^1 ds \sqrt{(1-s)(1-\kappa^2 s)} \cos \left[a(\xi, x) \left(\sqrt{1-\kappa^2 s} - \kappa \sqrt{1-s} \right) \right], \quad (35)$$

with shorthand notation $a(\xi, x) = (\omega_L / \epsilon_0) \sqrt{1 + \xi x}$. With substitution $s = 1 - \frac{1-\kappa^2}{\kappa^2} \sinh^2 \alpha$, S is brought to the form

$$S(\xi, x) = \frac{4(1-\kappa^2)^2}{\kappa^3} \int_0^{\alpha_0} d\alpha (\sinh \alpha \cosh \alpha)^2 \cos \left[a(\xi, x) \sqrt{1-\kappa^2} e^{-\alpha} \right], \quad (36)$$

where $\sinh \alpha_0 = \kappa / \sqrt{1-\kappa^2}$. For $a(\xi, x) \gg 1$, the integral is dominated by the upper limit, and for thin shells, $1 - \kappa \ll 1$, corresponding to $\alpha_0 > 1$, can be evaluated as

$$S \approx -4 \frac{\sin(a \sqrt{1-\kappa^2} e^{-\alpha_0})}{a \sqrt{1-\kappa^2} e^{-\alpha_0}} = -4 \frac{\sin[a(1-\kappa)]}{a(1-\kappa)}. \quad (37)$$

With the above S and after change of variable $t = \sqrt{1 + \xi x}$, the expression for $G(\xi)$ takes the form

$$G(\xi) = -\frac{8}{\xi D} \int_{t_-}^{t_+} dt t^3 \sin(tD), \quad (38)$$

where $t_{\pm} = \sqrt{1 \pm \xi/2}$, and we introduced $D = (1 - \kappa) \omega_L / \epsilon_0 = \omega_L d / v_F$. Note that even though for $\xi \ll 1$ the integration interval is small, the integrand is still an oscillating function

since $D \gg 1$ and so the product $D\xi$ can be arbitrary. In this case, a straightforward evaluation yields

$$G(\xi) = -4 \frac{\sin D}{D} \frac{\sin(\xi D/4)}{\xi D/4}. \quad (39)$$

Putting all together, we finally obtain

$$\mathcal{Q}_L = \frac{R_2^2 E_F^2}{\pi^2 \omega_L^2} [\mathcal{E}_L^2(R_2) + \kappa^2 \mathcal{E}_L^2(R_1) - 2\kappa^2 \mathcal{E}_L(R_1) \mathcal{E}_L(R_2) G]. \quad (40)$$

The last term in the above expression oscillates as a function of κ . Oscillations are caused by the change of electron-hole state parity as its energy changes with d , and reveal themselves through the interference between electron scatterings from outer and inner surfaces. The oscillations period depends weakly on shell thickness through $\omega_L(\kappa)$, and their amplitude slowly dies out with increasing d . Note that although the interference correction, Eq. (30), was obtained for thin shells, the full dissipated power $\mathcal{Q}_L$, Eq. (40) remains a good approximation in the entire range of κ , since for small κ the interference term is also small.

V. LANDAU DAMPING IN NANOSHELLS

We now turn to SP LD rate, $\Gamma_L = \mathcal{Q}_L/\mathcal{U}_L$, with $\mathcal{Q}_L$ and $\mathcal{U}_L$ given by Eqs. (19) and (40). To simplify the analysis, consider the case of a metal shell in vacuum ($\varepsilon_c = \varepsilon_d = 1$). Then we obtain

$$\Gamma_L = \left(\frac{4E_F^2}{\pi\omega_p^2} \right) \left[\frac{-e^2}{\varepsilon_m(\omega_L)R_2} \right] \frac{1 + \kappa^2 q_L^2 - 2\kappa^2 q_L G}{1/(L+1) + \kappa^3 q_L^2/L}, \quad (41)$$

where $q_L = \mathcal{E}_L(R_1)/\mathcal{E}_L(R_2)$ is the ratio of electric fields at the boundaries,

$$q_L = \frac{L\kappa^L - (L+1)\eta_L}{\kappa[L - (L+1)\eta_L\kappa^{L+1}]} = \frac{\kappa^{L-1}A_L}{A_L - (1 - \kappa^{2L+1})(L+1)/(2L+1)}. \quad (42)$$

The expression (41) is our central result. The SP LD rate is proportional to the energy of Fermi sea electron-hole pair created by SP (second factor), multiplied by the phase space of the transition (first factor). The last factor describes the relative contribution of the nanoshell inner surface and includes the interference correction. Importantly, the electron-hole Coulomb potential is screened by metal dielectric function at *SP frequency*.

For solid nanoparticle ($\kappa = 0$), the plasmon eigenfrequency is determined from $L\varepsilon_m(\omega_L) + L + 1 = 0$, and we recover the result of Kawabata and Kubo,

$$\Gamma_L^p = \left(\frac{4E_F^2}{\pi\omega_p^2} \right) \frac{e^2 L}{R_2} = \frac{3L}{4} \frac{v_F}{R_2}. \quad (43)$$

Note that although the r.h.s. resembles the level spacing (at constant l) in spatially-confined system, this resemblance is *coincidental* because Eq. (43) contains no information about electron energy spectrum.

For thin nanoshell, the situation is drastically different. The redshift of plasmon energy, ω_L implies large (negative) value of $\epsilon_L(\omega_L)$, which leads to *overscreening* of the electron-hole Coulomb energy. As a result, Γ *vanishes* in the thin shell limit. The precise behavior of Γ_L can be deduced from $(1 - \kappa) \ll 1$ asymptotics, $q_L \approx -L/(L + 1)$ and $\epsilon_m \approx -A_L^{-1} \approx -(1 - \kappa)^{-1}(2L + 1)/L(L + 1)$, yielding

$$\Gamma_L \approx \frac{v_F d}{R_2^2} \frac{3L(L + 1)}{4(2L + 1)^2} [1 + 2L(L + 1)(1 + G)], \quad (44)$$

i.e., Γ_L decreases *linearly* with shell thickness.

In Figs. 2 and 3 we show the calculated LD for dipole SP as well as the corresponding quality factors in the entire range of aspect ratios for Au nanoshells in vacuum with outer radii 30 nm and 10 nm, respectively. The decrease of Γ is accompanied by the increase of Q despite the SP frequency redshift for thin nanoshells. The asymptotic behavior of quality factor, $Q \propto d^{-1/2}$, follows from the weaker dependence of the nanoshell SP frequency, $\omega_{sp} \propto \sqrt{d}$. For small d , both Γ and Q exhibit oscillations as a function of d , with period $d_L = v_F T_L$, where T_L is the SP period. The latter itself weakly depends on d , resulting in a slow increase of oscillation period with d , however undetectable due to the reduction of their amplitude. The oscillations are quite pronounced for smaller overall nanoshell size and could be observable for typical experimental range of aspect ratios (0.6-0.8). Note that these oscillations should be distinguished from those observed in solid NP [12]; in the latter case, the oscillations originate from size-quantization of electron energy levels in a confined nanostructure, while here they are due to quantum interference of electron wave-functions at different nanoshell boundaries.

VI. CONCLUSION

In summary, we performed the first quantum-mechanical calculation of surface plasmon Landau damping in a metal nanoshell, and found that it vanishes in the thin shell limit. The physical origin of a long bright SP lifetime is that its electric field magnitude inside a thin metal shell is reduced. Obviously, such a situation is not limited to nanoshells with

spherical symmetry considered here, but can take place in other structures too. Therefore, the quantum-size limitations on plasmon lifetime in small metal nanostructures are, in fact, spurious and can be avoided by an appropriate choice of geometry.

This work was supported by the NSF under Grant Nos. DMR-0906945 and HRD-0833178.

-
- [1] A. Kawabata and R. Kubo, J. Phys. Soc. Jpn. **21**, 1765 (1960).
 - [2] U. Kreibig and M. Vollmer, *Optical Properties of Metal Clusters* (Springer, 1995), and references therein.
 - [3] J. Zhao, X. Zhang, C. Yonzon, A. J. Haes, and R. P. Van Duyne, *Nanomedicine* **1**, 219 (2006), and references therein.
 - [4] K. Li, M. I. Stockman, D. J. Bergman, Phys. Rev. Lett. **91**, 227402 (2003).
 - [5] D. J. Bergman, and M. I. Stockman, Phys. Rev. Lett. **90**, 027402 (2003).
 - [6] V. N. Pustovit and T. V. Shahbazyan, Phys. Rev. B **73**, 085408 (2006).
 - [7] R. D. Averitt, D. Sarkar, and N. J. Halas, Phys. Rev. Lett. **78**, 4217 (1997).
 - [8] S. L. Westcott, J. B. Jackson, C. Radloff, and N. J. Halas, Phys. Rev. B **66**, 155431 (2002).
 - [9] G. Raschke, S. Brogl, A. S. Susa, A. L. Rogach, T. A Klar and J. Feldmann, *Nano Letters* **4**, 1853 (2004).
 - [10] C. L. Nehl, N. K. Grady, G. P. Goodrich, F. Tam, N. J. Halas, and J. H. Hafner, *Nano Letters* **4**, 2355 (2004).
 - [11] G.D. Mahan, *Many-Particle Physics* (Plenum, New York, 1990).
 - [12] R. A. Molina, D. Weinmann, and R. A. Jalabert, Phys. Rev. B **65**, 155427 (2002).

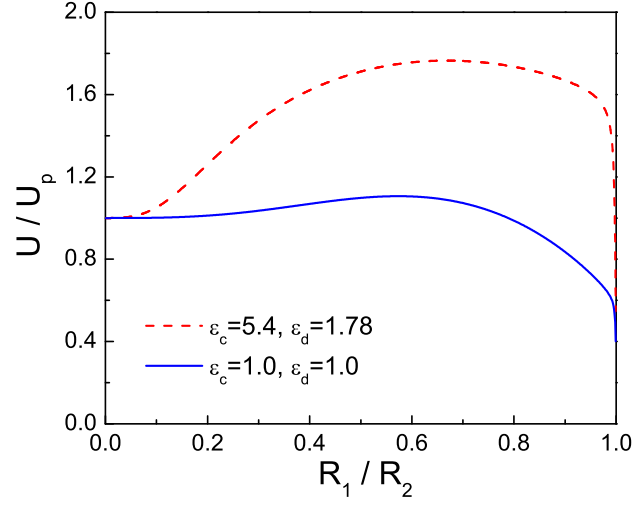


FIG. 1: SP energy in Au nanoshell in vacuum (solid line) and in Au₂S/Au core-shell particle in water (dashed line) relative to solid nanoparticle of the same overall size.

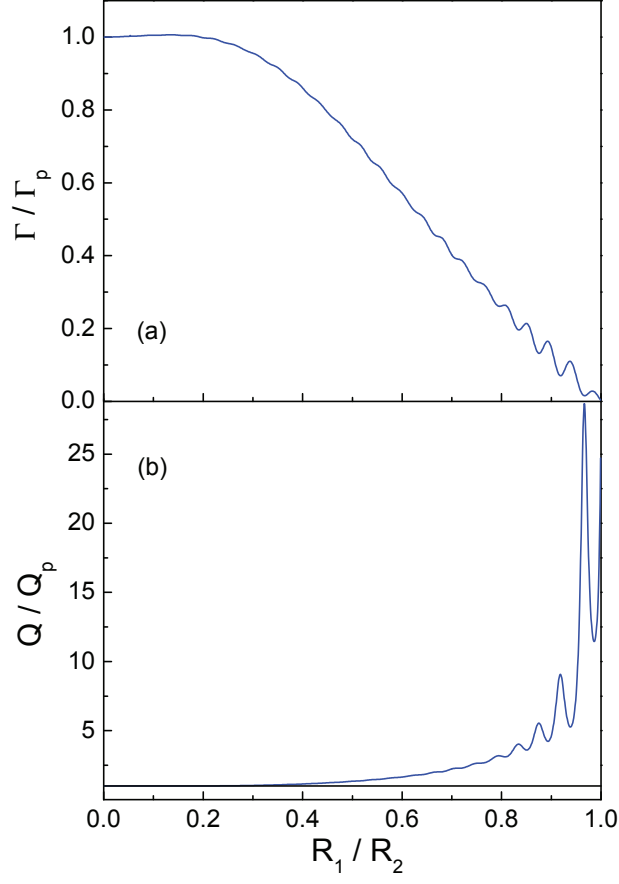


FIG. 2: Calculated SP LD rate (a) and quality factor (b) for Au nanoshell with outer radius $R_2 = 30.0$ nm in vacuum relative to solid Au NP of the same overall size. Solid horizontal line of unit height is added for comparison with solid NP.

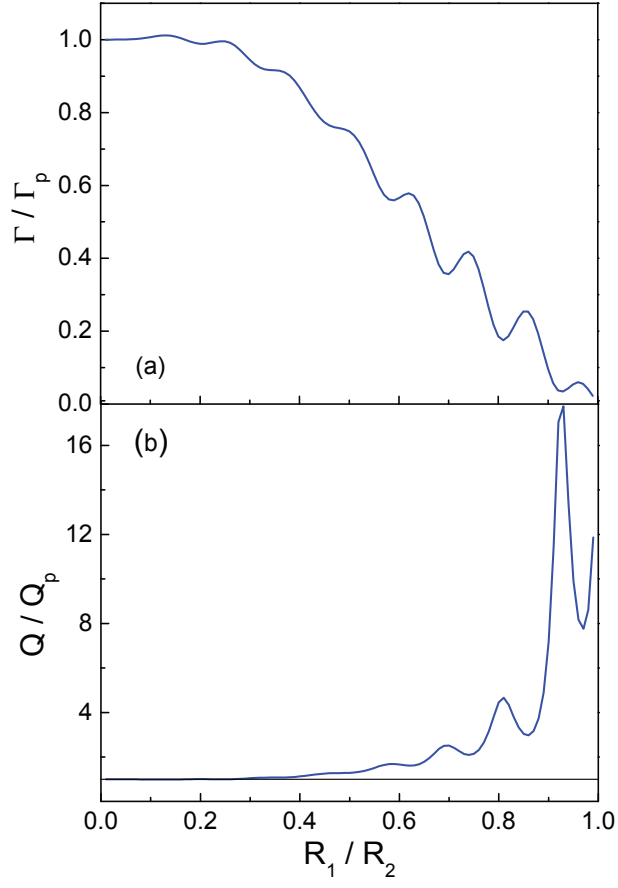


FIG. 3: Same as in Fig. 2, but with $R_2 = 10.0$ nm.